

TOMBO™ BRAND

Elastomer O-Rings

General Catalog of High Performance Elastomer O-Rings




BLAZER™
SERIES
High Performance Elastomer Parts

NICHIAS elastomer O-rings meet the stringent requirements for components used in various industrial field, by means of versatile functionality and a complete product lineup.


Our high performance elastomer with properties, such as purity and resistance against heat, chemical, wear, plasma and ozone, are suitable for various conditions of use.

Contents

■ BLAZER™ S2 NEW	3
■ BLAZER™ FC NEW	5
■ BLAZER™ FE NEW	5
Selection guide to elastomer O-rings used in a semiconductor manufacturing process	7
Comparison of characteristics of high performance elastomer O-rings	8
■ BLAZER™ NEXT	9
■ BLAZER™ A	10
■ PERFLUORO PFW™	10
■ PURE RUBBER™	11
■ FLUORO ELASTOMER FB	12
■ FLUORO PLUS	13
■ FLUORO ELASTOMER FA	13
■ Large O-rings	14
Chemical resistance of various elastomer materials	15
Physical properties of elastomer materials	17
Product No. (TOMBO™ No.) indication method	18
Allowable manufacturing dimensions	18
To ensure safe use	18

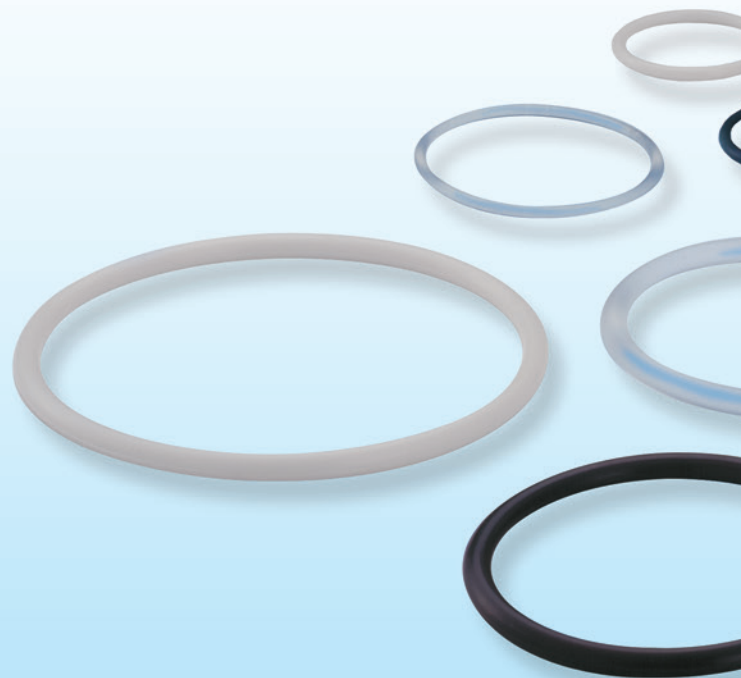

Correspondence table by resistance

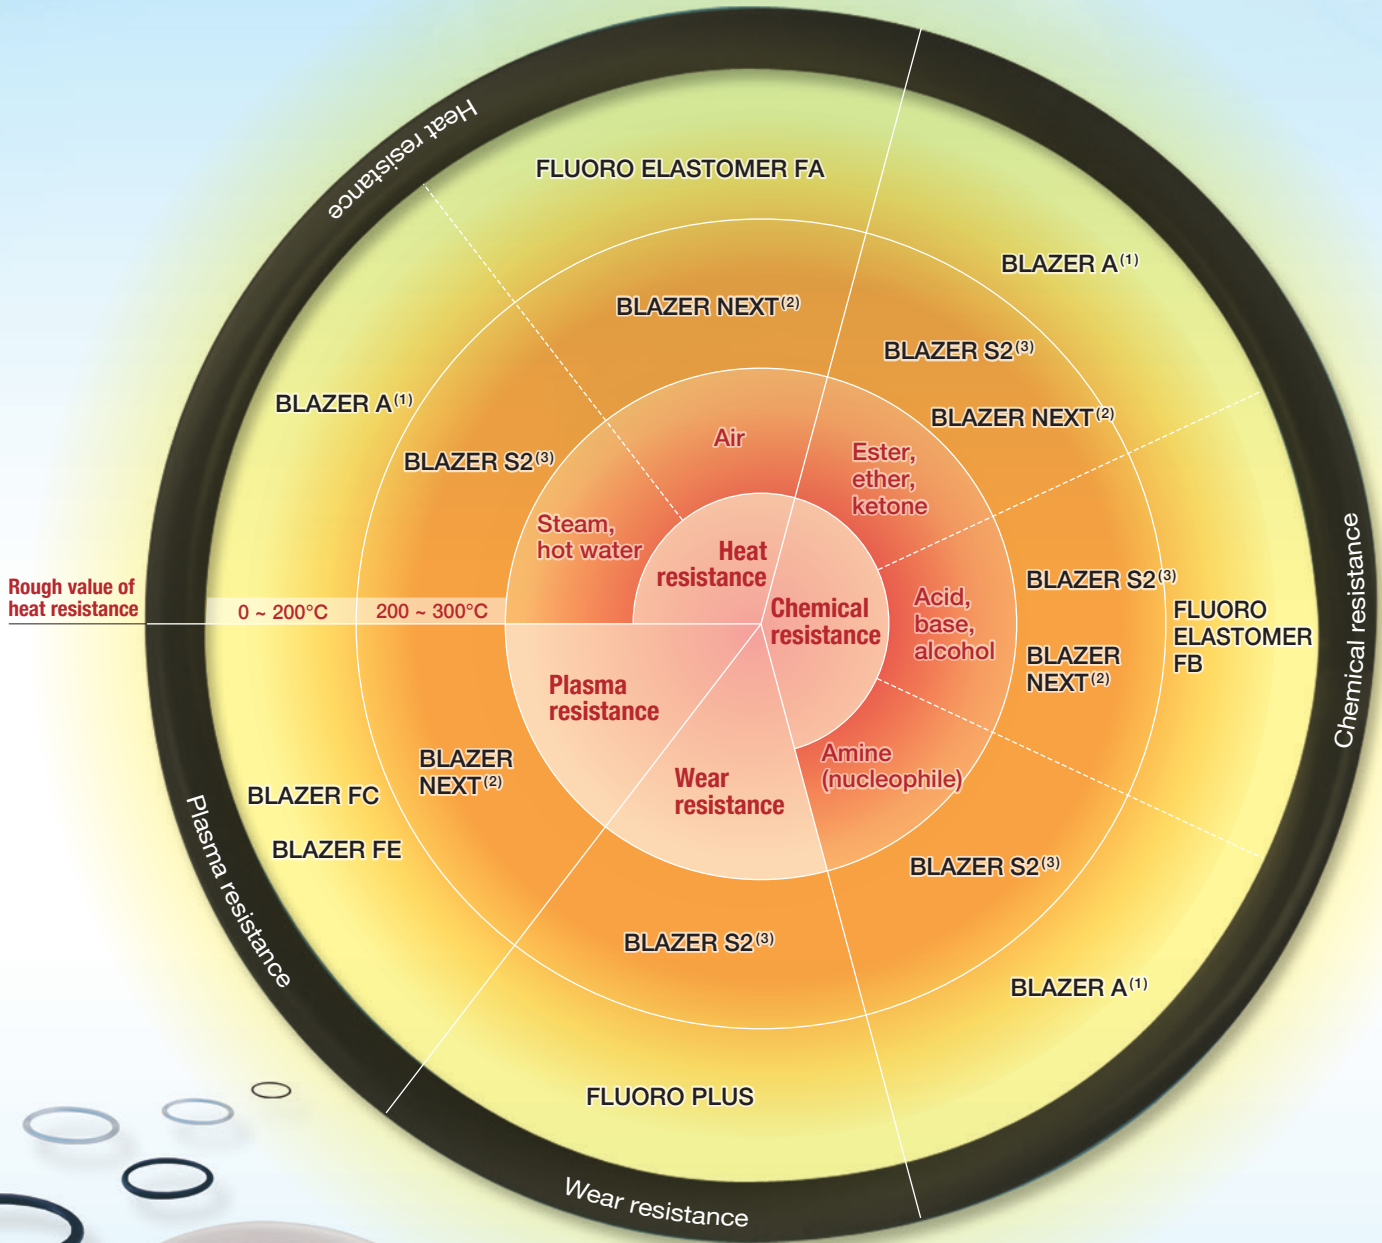

Note : (1) The rough value of heat resistance of BLAZER™ A is 210 °C
 (2) The rough value of heat resistance of BLAZER™ NEXT is 335 °C
 (3) The rough value of heat resistance of BLAZER™ S2 is 320 °C



BLAZER™ O-ring-S2

TOMBO™ No.2675-S2

BLAZER™ S2, a PERFLUORO ELASTOMER, exhibits stable sealing performance when exposed to high-temperature steam or a nucleophilic agent. The new cross-linking agent and our unique blending technology are used for this, resulting in greatly improved steam resistance, RGD (rapid gas decompression) resistance, and toughness at high-temperature.

Features

Rough value of heat resistance: 320°C

Standard hardness (Duro A): 80

Offers the broadest chemical compatibility, e.g., better resistance amines, esters, ethers, ketones, acids, bases, hydrocarbons, chlorine-based solvents, hot water and steam.

Provides excellent RGD resistance so parts maintain sealing properties and equipment life is extended.

Excellent toughness at high temperatures.



Applications

Can be used as a seal in valves, pumps, turbo machinery, painting machines, centrifuges, agitators, analyzers, reaction furnaces, and the like.

Steam resistance test results

Inspected in NICHIAS





Testpiece		BRAZER™ S2	BRAZER™ S	Competitor's	
320°C	72hours	Before			
		After			

In an environment of high-temperature steam, competitor's undergoes hydrolysis and melt. In contrast, BLAZER™ S2 does not undergo hydrolysis.

Rapid pressure reduction characteristics test results

When the pressure of this elastomer in a high pressure environment is reduced rapidly, the gas which had permeated the elastomer due to the high pressure swells as a result of the rapid pressure reduction, which may cause blistering of the elastomer. As a result of being subjected to a rapid pressure reduction, the BLAZER™ S2 is found to have 1 or 2 damage points, and compared to other companies' perfluoro-elastomer, it is suitable for use in an environment in which the pressure is rapidly reduced.

Inspected in KOBELCO Research Institute, Inc.

Testpiece	BRAZER™ S2	BRAZER™ S	Competitor's	BRAZER™ NEXT
Cross-section O-rings after test				
Damage rating	1 or 2	1 or 2	1 or 2	3

Evaluation criteria of the number of damage points

Number of points	Condition inside the sample after the test
1	No damage
2	No more than 1 crack or blister on the cut face
3	Cracks or blister on no more than 50% of the cut face
4	Cracks or blister on more than 50% of the cut face

● Test conditions

Heat the pressure vessel, then pressure-feed CO₂, and leave standing.

Temperature: 100°C

Pressure: 15 MPa


Fluid: Supercritical CO₂

Holding period: 24 hrs

Pressure reduction rate: 7 MPa/min

Testpiece: Thickness φ3.53 mm × 30 mm Strip

Evaluation results of resistance against compression force (at 300°C in an air)

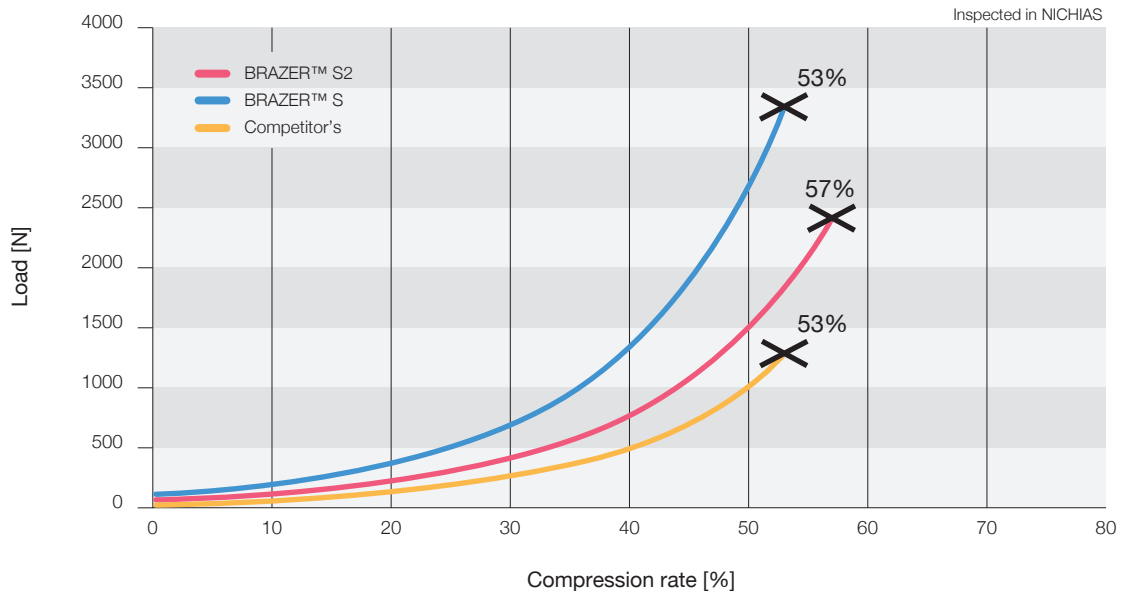

● Test conditions

Testpiece: Thickness φ3.53 mm × 50 mm Strip

Atmosphere: Air

Compression rate: 0.1 mm / min

Temperature: 300 °C

BLAZER™ S2 has excellent resistance against compression force at 300°C



The BLAZER™ FC is a special FLUORO ELASTOMER (special FKM) O-ring intended for use in a plasma CVD unit which is a component unit of a semiconductor or LCD manufacturing unit. It exhibits high resistance to F-type and Cl-type plasma.



Features

Rough value of heat resistance: 200°C

Standard hardness (Duro A): 60

By using our own blending technology, the reduction of weight of the elastomer due to the plasma can be reduced and also made the cost of the product considerably less than that of PERFLUORO ELASTOMER.

This product has excellent non-adhesiveness, enabling it to be used effectively even on moving parts.

Contains only a small amount of metal, so particle issues are reduced.

Applications

Sealing of plasma CVD units



The BLAZER™ FE is a special FLUORO ELASTOMER (special FKM) O-ring intended for use in a plasma etching unit which is a component unit of a semiconductor or LCD manufacturing unit. It exhibits high resistance to O₂ type plasma.



Features

Rough value of heat resistance: 200°C

Standard hardness (Duro A): 60

By using our own blending technology, the reduction of weight of the elastomer due to the plasma can be reduced and also made the cost of the product considerably less than that of PERFLUORO ELASTOMER.


This product has excellent non-adhesiveness, enabling it to be used effectively even on moving parts.

Contains only a small amount of metal, so particle issues are reduced.

Applications

Sealing of plasma etching units

[Percentage reduction of weight after 120 minutes]

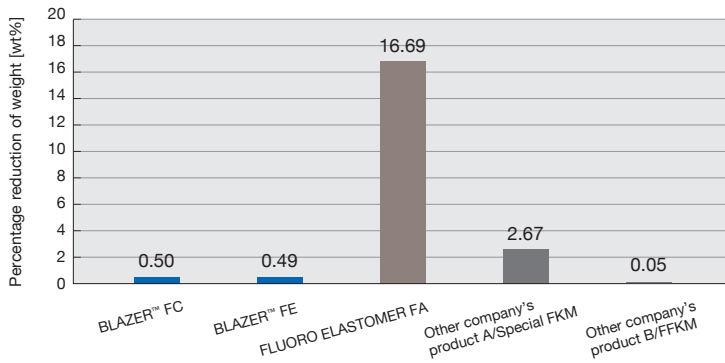

● Test conditions

Unit: Surface wave plasma etching unit
 Testpiece: Thickness ϕ 3.53 mm \times 30 mm Strip
 Type of gas: O₂ (2000 sccm) + CF₄ (40 sccm)
 Pressure: 133 Pa
 Output: 2000 W
 Stage cooling water set temperature: 30°C
 Exposure time: 120 minutes

[Exterior observation]

Inspected in NICHIAS











Product name	BLAZER™ FC	BLAZER™ FE	FLUORO ELASTOMER FA	Other company's product B/FFKM
Crack occurrence time [minutes]	40	No cracks	20	40
Before exposure				
After 20 minutes				
After 40 minutes				
After 60 minutes				
After 120 minutes				



● Test conditions

Unit: Surface wave plasma etching unit
 Testpiece: O-ring AS568-214 (Thickness ϕ 3.53 mm \times I. D. 25.00 mm)
 Type of gas: O₂ (2000 sccm) + CF₄ (40 sccm)
 Pressure: 133 Pa
 Output: 2000 W
 Stage cooling water set temperature: 30°C
 Exposure time: 2.0 hrs
 Percentage elongation: 5%
 Exterior observation: At 5-minute intervals to 20 minutes; Subsequently, at 10-minute intervals to 120 minutes

Selection guide to elastomer O-rings used in a semiconductor manufacturing process

Process	Equipment	Applications	Recommended products	Characteristics of materials
Oxidation and diffusion 	Oxidation and diffusion furnace	Furnace body seal	BLAZER™ NEXT	<ul style="list-style-type: none"> ● Heat resistance ● Low-discharge gas
			FLUORO ELASTOMER FA	* Standard fluoro-elastomer
Lithography Resist coating  Exposure  Developing 	Coater	Chemical line seal Baking unit	BLAZER™ A	<ul style="list-style-type: none"> ● Solvent resistance ● Purity
	Stepper	Purge chamber seal	FLUORO ELASTOMER FA	<ul style="list-style-type: none"> ● Wear resistance ● Non-adhesiveness
	Developer	Chemical line seal	BLAZER™ A	<ul style="list-style-type: none"> ● Solvent resistance ● Purity
Etching Dry etching  Ashing 	Plasma etching unit	Seal in chamber (Chamber lid, gate valve, peephole, etc.)	BLAZER™ FE	<ul style="list-style-type: none"> ● Plasma resistance
	Plasma ashing unit		PERFLUORO PFW™	<ul style="list-style-type: none"> ● Plasma resistance
			BLAZER™ NEXT	<ul style="list-style-type: none"> ● Heat resistance ● Low-discharge gas
			BLAZER™ FE	<ul style="list-style-type: none"> ● Plasma resistance
			PERFLUORO PFW™	<ul style="list-style-type: none"> ● Plasma resistance
	BLAZER™ NEXT		<ul style="list-style-type: none"> ● Heat resistance ● Low-discharge gas 	
Ion implantation 	Thermal diffusion furnace Ion implanting unit	Seal in chamber	BLAZER™ NEXT	<ul style="list-style-type: none"> ● Heat resistance ● Low-discharge gas
			FLUORO ELASTOMER FA	* Standard fluoro-elastomer
Thin-film forming 	Metal CVD unit Plasma CVD unit Sputtering unit	Seal in chamber (Chamber lid, peephole, etc.)	BLAZER™ FC	<ul style="list-style-type: none"> ● Plasma resistance
			BLAZER™ NEXT	<ul style="list-style-type: none"> ● Heat resistance ● Low-discharge gas
			FLUORO ELASTOMER FA	* Standard fluoro-elastomer
Flattening 	CMP unit	Seal in chamber Chemical line seal	BLAZER™ A	<ul style="list-style-type: none"> ● Chemical resistance ● Purity
			FLUORO ELASTOMER FB	<ul style="list-style-type: none"> ● Acid resistance ● Purity
Washing 	Washing unit	Chemical line seal Filter seal	BLAZER™ A	<ul style="list-style-type: none"> ● Chemical resistance ● Purity
			FLUORO ELASTOMER FB	<ul style="list-style-type: none"> ● Acid resistance ● Purity

Comparison of characteristics of high performance elastomer O-rings

Elastomer O-rings for a wet process

Elastomer O-rings used in various processes such as lithography, washing and wet etching are required to have not only chemical resistance and purity but also ozone resistance, non-adhesiveness, and other properties, depending upon the particular application.

Characteristics that are used	Product name	Color	Rough value of heat resistance	Chemical resistance					Purity (eluted metal)	Non-adhesiveness
				Oil resistance	Acid resistance	Alkali resistance	Solvent resistance	Ozone resistance		
Chemical resistance	BLAZER™ A	Black	210℃	◎	◎	◎	◎	◎	◎	○
	FLUORO ELASTOMER FB	Black	200℃	◎	◎	○	○	○	◎	○
Ozone resistance	BLAZER™ A	Black	210℃	◎	◎	◎	◎	◎	◎	○
	PURE RUBBER™	Transparent	150℃	◎	◎	○	○	◎	◎	△
Non-adhesiveness	FLUORO PLUS™	Black	200℃	◎	○	△	△	△	△ (Mg, Ca)	◎
General purpose product	FLUORO ELASTOMER FA	Black	200℃	◎	○	△	△	△	△ (Mg, Ca)	○

■ Method of reading evaluation symbols: The symbols ◎, ○, and △ mean “most suitable,” “suitable,” and “unsuitable,” in that sequence. Note, however, that the evaluations in this table are intended only as a rough guide, and we are unable to guarantee the performance of the products for individual applications. For data concerning the resistance to various kinds of chemicals, refer to Page 15-16.

* For details of general properties, refer to Page 17. For product No. indication method and allowable manufacturing dimensions, refer to Page 18.

O-rings for a dry process

Elastomer O-rings intended for use in a dry process such as dry etching, ashing and CVD are required to have higher heat resistance and plasma resistance, and also low-discharge gas characteristics.

Characteristics that are used	Product name	Color	Rough value of heat resistance	Plasma resistance			Low-discharge gas characteristics	Vacuum sealing performance	Non-adhesiveness
				Oxygen	Fluorine	Chlorine			
Heat resistance	BLAZER™ NEXT	Black	335℃	◎	◎	◎	◎	○	○
Plasma resistance	PERFLUORO PFW™	White	200℃	◎	◎	◎	○	○	○
	BLAZER™ NEXT	Black	335℃	◎	◎	◎	◎	○	○
	BLAZER™ FC	Black	200℃	○ ~ ◎			○	○	○
	BLAZER™ FE	Black	200℃	○ ~ ◎	○	○	○	○	○
Non-adhesiveness	FLUORO PLUS™	Black	200℃	△	○	△	○	△	◎
General purpose product	FLUORO ELASTOMER FA	Black	200℃	△	○	△	○	◎	○

■ Method of reading evaluation symbols: The symbols ◎, ○, and △ mean “most suitable,” “suitable,” and “unsuitable,” in that sequence. Note, however, that the evaluations in this table are intended only as a rough guide, and we are unable to guarantee the performance of the products for individual applications. When actually using a product, it is recommended that you perform a check using a test carried out under actual conditions.

* For details of general properties, refer to Page 17. For product No. indication method and allowable manufacturing dimensions, refer to Page 18.



BLAZER™ NEXT

TOMBO™ No.2670 -BNX

BLAZER™ NEXT is PERFLUORO ELASTOMER which has excellent heat resistance and plasma resistance. It has good sealing performance even under severe environments, which is difficult to realize using other elastomer materials.

Features

Rough value of heat resistance: 335°C

Standard hardness (Duro A): 76

Undergoes little compressive permanent strain when subjected to high temperature, and can therefore be expected to realize stable sealing performance over a long period.


Applications

Sealing of heat treatment units for manufacturing semiconductors and LCD concerning which heat resistance is particularly necessary (annealing furnaces, LPCVD units, etc.)

Sealing of units, piping and valves used in various industrial fields



Chemical structure (PERFLUORO ELASTOMER overall)

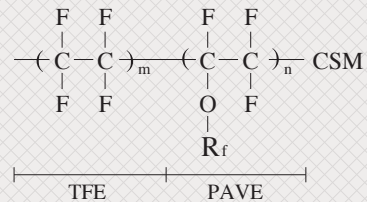

CSM = Cross-linked site monomer

350°C free heating test

Inspected in NICHIAS

	BLAZER™ NEXT	Other company's product A	Other company's product B	Other company's product C
Before heating				
After heating for 72 hours				


* This data does not imply that use at 350°C is recommended.

⚠ Precaution for use

BLAZER™ NEXT undergoes large thermal expansion, so it may sometimes be subjected to excessive compression when used at high temperature (250°C or higher). Care must be taken, particularly when the compressibility (at normal temperature) is 20% or more. For details, please contact us.

Compressive permanent strain test results

Inspected in NICHIAS

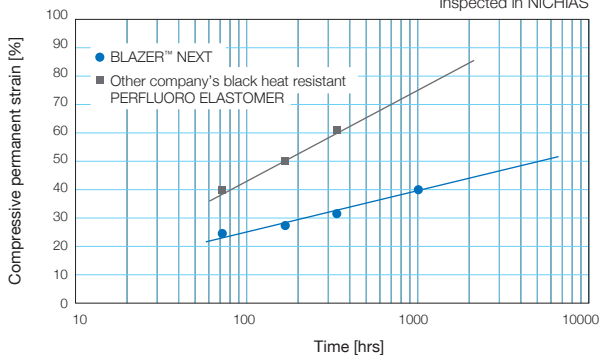


● Test conditions

Measuring jig: Refer to the figure below.

Testpiece: O-ring (AS568-214; Thickness φ3.53 mm × I. D. 25.0 mm)

Heating temperature: 300°C

Compressibility: 19% (at normal temperature), 25% (when heated)

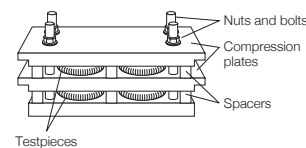

$$\text{Compressive permanent strain (\%)} = \frac{t_0 - t_1}{t_0 - t_2} \times 100$$

t₀: Original thickness of testpiece

t₁: Thickness 30 minutes after the testpiece is removed from the compressor unit

t₂: Thickness of the spacer

The high-temperature compressive permanent strain of the BLAZER™ NEXT is smaller than that of other company's black heat resistant PERFLUORO ELASTOMER (heat resistance temperature mentioned in catalog: 300°C), so this type of elastomer can be expected to realize stable sealing performance over a long period.



**BLAZER™
O-ring-A**

TOMBO™ No.2675-A

This type of elastomer has excellent chemical resistance. Particularly, it is highly resistant to polar solvents such as amines and organic acids, which cannot be realized by other kinds of FLUORO ELASTOMER. It produces little elution of metal, and is suitable for applications which require both chemical resistance and purity.



Features

Rough value of heat resistance: 210°C

Standard hardness (Duro A): 75

Has excellent chemical resistance, enabling it to be used with almost all chemicals (excluding fluorine-based solvents).

Almost no metal is eluted into the chemical used.

Applications


Sealing of washing units, coaters/developers, wet etching units, filters, etc.

Elastomer O-rings

**PERFLUORO
PFW™**

TOMBO™ No.2670-PFW

Has excellent plasma resistance, and is used on dry etching units for manufacturing semiconductors.

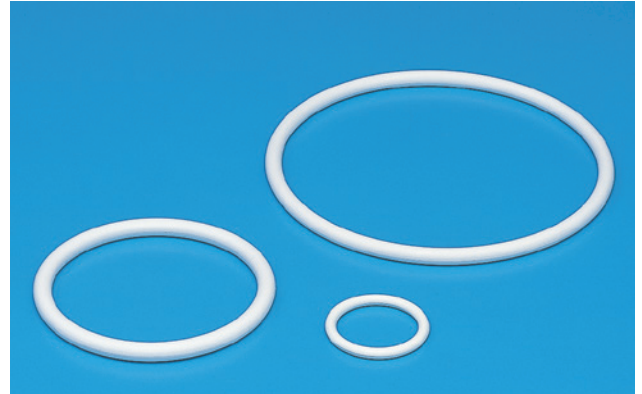

Features

Rough value of heat resistance: 200°C


Standard hardness (Duro A): 70

Has excellent plasma resistance, and undergoes little reduction of weight when exposed to plasma.

Applications

Sealing of plasma etching units, plasma CVD units, and so on

Results of measuring metal elution

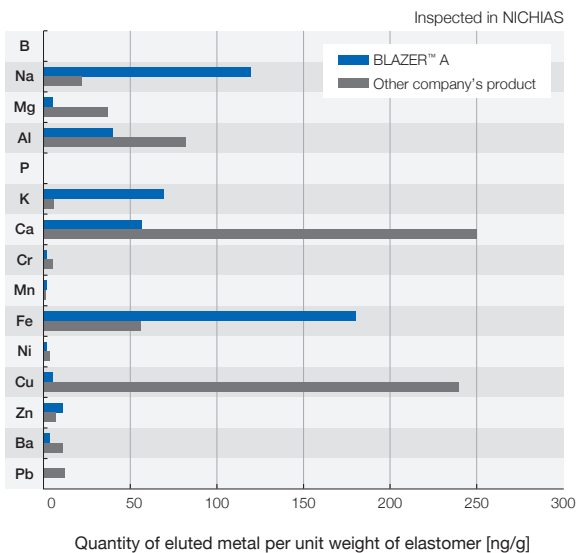

The results indicate that because BLAZER™ A does not contain metal in its formulation, it produces only a very small amount of metal ions compared to other company's product.

● Test conditions

- Pre-washing: None
- Elution
 - Testpiece: O-ring AS568-214 (Thickness φ3.53 mm × I. D. φ25.00 mm)
 - Chemical: 3.6% hydrochloric acid 100 g
 - Temperature × Time: 25°C × 20 hours
- Analysis method: ICP-MS

PURE RUBBER is a transparent elastomer consisting of a polymer formed by bonding FLUORO ELASTOMER to fluoro-resin. It employs radiation cross-linking, so it does not contain a cross-linking agent. Also, it contains no fillers or other additives whatever. It thus features a high degree of cleanliness. In addition, the fluoro-resin grains bonded to each other inside the polymer result in excellent ozone resistance and chemical resistance.

Features

Rough value of heat resistance: 150°C

Standard hardness (Duro A): 60


Because this elastomer does not contain a cross-linking agent, fillers or other additives, there is almost no eluted material.

Because this product consists of FLUORO ELASTOMER and fluoro-resin, it has excellent ozone resistance and chemical resistance.

Applications

Sealing of washing unit, etc.

Conveying rollers for LCD manufacturing units

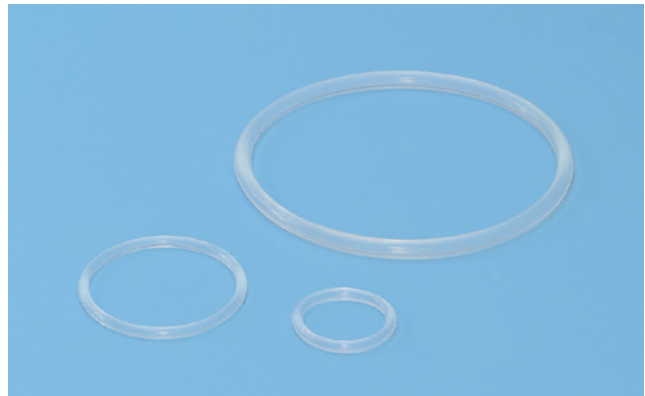

Chemical structure

Hard segment: ETFE

Soft segment: Ternary FKM

Ozone (wet atmosphere) exposure test results

Test conditions

Exposure atmosphere: 10% ozone gas + Saturated steam / Temperature: 23°C / Time: 20 weeks (1 week in the case of FLUORO ELASTOMER FA)

PURE RUBBER		Before exposure	After 20 weeks' exposure, there is almost no change in the external appearance or the surface adhesion.		After 20 weeks' exposure
FLUORO ELASTOMER FA		Before exposure	After 1 week's exposure, the surface has dissolved, and there is adhesion.		After 1 week's exposure

Inspected in NICHIAS

FLUORO ELASTOMER FB is 3-way FLUORO ELASTOMER with improved chemical resistance realized by our independently developed blending technology. It has excellent resistance to hot acids and steam, which cannot be realized with general purpose FLUORO ELASTOMER. In addition, the amount of eluted material is very small, resulting in high performance fluoro-elastomer which has a high degree of purity.

Features

Rough value of heat resistance: 200°C

Standard hardness (Duro A): 70

This product can be used in an environment consisting of hot inorganic acid, steam, sodium hydroxide, and other substances that corrode general purpose FLUORO ELASTOMER.


Almost no metal is eluted into the chemical used.

Applications


Washing units, wet etching units, filters, etc.



Chemical structure

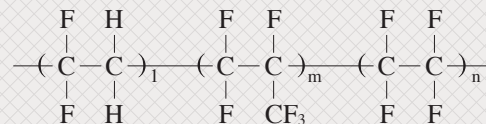

Results of measuring eluted metal

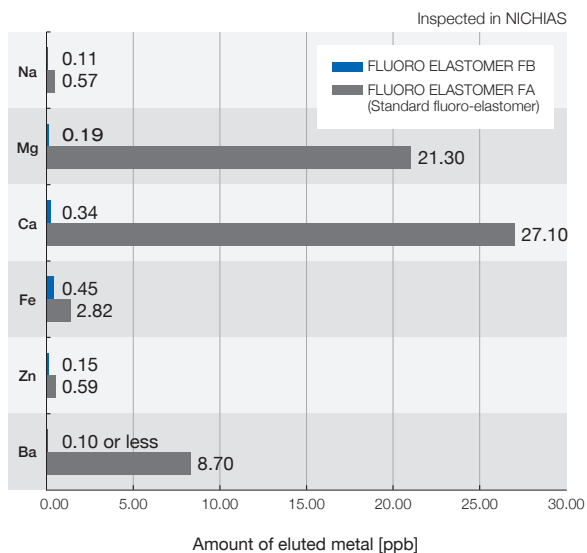

Because FLUORO ELASTOMER FB does not contain metal in its formulation, the elution of metal ion is extremely small compared to that of FLUORO ELASTOMER FA, as indicated by the test results.

Test conditions

- Pre-washing: The testpiece was washed in a 5% solution of hydrofluoric acid, and then washed in ultra-pure water.
- Elution
 - Testpiece: O-ring JIS P16
(Thickness φ2.4 mm × I. D. φ15.8 mm)
 - Chemical: 50% solution of hydrofluoric acid 300 g
 - Temperature × Time: 24°C × 72 hours (3 days)
- Analysis method: ICP-MS

Low friction, non-adhesive
FLUORO ELASTOMER

Low friction


Non-adhesiveness

Elastomer O-rings

FLUORO PLUS™

TOMBO™ No.2670-FA-F

FLUORO PLUS is a special type of FLUORO ELASTOMER which has greatly improved friction resistance and non-adhesiveness while retaining the chemical resistance and heat resistance of FLUORO ELASTOMER. FLUORO PLUS differs from a skin coating in that it is treated using a surface modification method, enabling its characteristics to be maintained for a long period, and also preventing separation of the surface layer.

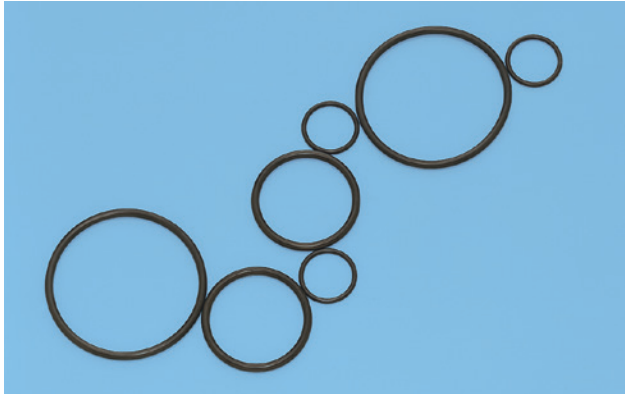

Features

Rough value of heat resistance: 200°C

Standard hardness (Duro A): 70

The coefficient of friction is approximately 1/2 of that of standard FLUORO ELASTOMER.

The adhesiveness to metal is approximately 1/5 of that of standard FLUORO ELASTOMER.

Because the surface is treated using a modification method, the surface layer will not separate.

Applications

For sealing parts that slide intermittently, and also parts that are repeatedly opened and closed (Sealing various control valves)

Places where conventional elastomer sticks fast to metal, causing maintenance performance to deteriorate.



Precaution for use

Compared to FLUORO ELASTOMER FA, FLUORO PLUS has inferior conformability with the mating face, so do not use it for a high vacuum seal.


General purpose FLUORO ELASTOMER

Elastomer O-rings

FLUORO ELASTOMER FA

TOMBO™ No.2670-FA

FLUORO ELASTOMER FA is equivalent to FKM-70 in JIS B 2401 (O-rings). It is a 2-way FLUORO ELASTOMER O-ring which has excellent heat resistance, oil resistance, and vacuum sealing ability.

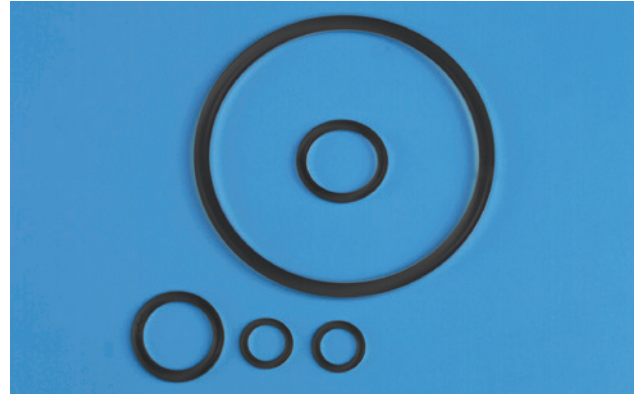

Features


Rough value of heat resistance: 200°C

Standard hardness (Duro A): 70

Applications

Sealing of vacuum equipment, heat treatment equipment, and so on.


Chemical structure

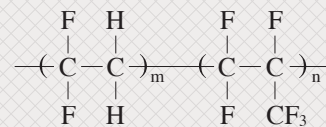

Non-adhesiveness

FLUORO PLUS vs FLUORO ELASTOMER FA

Inspected in NICHIAS

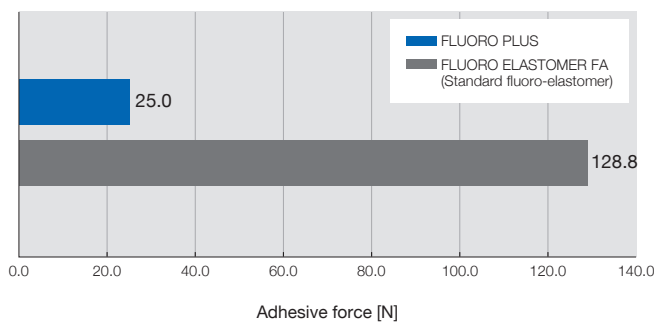


Test conditions

Testpiece: O-ring JIS P26
(Thickness φ3.5 mm × l. D. φ25.7 mm)

Compression ratio: 25%


Flange material: Aluminum

Heating conditions: 200°C × 22 hours



Large O-rings

Various types of original high performance elastomer can be joined together during the molding process. By molding two or more O-rings separately, and then joining them together and vulcanizing them, a large O-ring can be made without any need to fabricate a special die for each size of O-ring. This in turn enables the delivery time to be reduced.

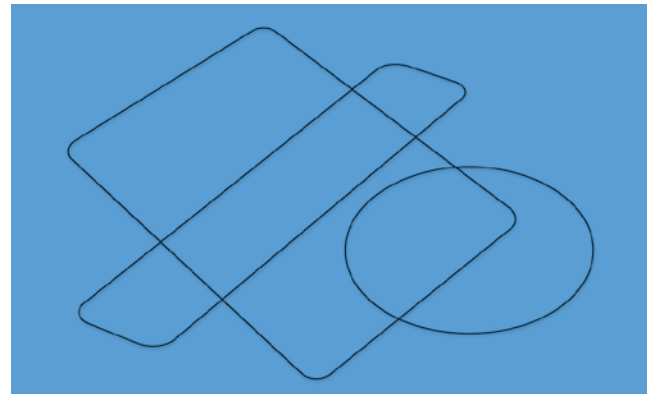

Features

I.D. can be set freely provided that it is within the allowable range of fabrication.

The delivery period for the part corresponding to die fabrication can be reduced.

The cost of die fabrication can be reduced.

Applications

Sealing of large LCD manufacturing units

Allowable range of fabrication

Product name	Thickness (mm)									I. D. that can be fabricated (mm)
	3.1	3.53	4.0	5.33	5.7	6.0	6.98	8.4	10.0	
BLAZER™ NEXT	—	○	—	○	○	—	○	○	○	400 or more
BLAZER™ S2	—	○	—	○	○	—	○	○	○	400 or more
BLAZER™ A	—	○	—	○	○	—	○	○	○	400 or more
BLAZER™ FC	—	○	—	○	○	—	○	○	○	400 or more
BLAZER™ FE	—	○	—	○	○	—	○	○	○	400 or more
PURE RUBBER™	○	○	○	○	○	○	○	○	○	50 (Thickness 6.0 or less) or more 100 (Thickness 6.99 – 8.4) or more 150 (Thickness 10.0) or more
FLUORO ELASTOMER FB	○	○	○	○	○	○	○	○	○	300 or more
FLUORO PLUS™	○	○	○	○	○	○	○	○	○	300 or more
FLUORO ELASTOMER FA	○	○	○	○	○	○	○	○	○	300 or more

* For thickness other than the above, please contact us.

Chemical resistance of various elastomer materials

This data concerns the chemical resistance of various elastomer materials which is judged overall based on the results of chemical immersion tests carried out in our test laboratory, existing publicized data, and actual data used. This chemical resistance data constitutes a very useful guide for selecting a elastomer material. However, regarding each individual application, there are conditions which cannot be created in our test laboratory, and it is not possible to guarantee the performance of the material for each customer's application. For this reason, if there is a possibility of damage or deterioration of the sealing parts causing major damage, it is recommended that prior to use you carry out tests under actual conditions and check the results.

Inspected in NICHIAS

Chemicals	Temperature [°C]	NICHIAS original high performance elastomer							Standard materials					
		BLAZER™ NEXT	BLAZER™ S2	BLAZER™ A	BLAZER™ FC	BLAZER™ FE	PURE RUBBER™	FLUORO ELASTOMER FB	FLUORO ELASTOMER FA	Silicone elastomer	Ethylene propylene elastomer	Chloroprene elastomer	Nitrile elastomer	
Acids	Hydrochloric acid 37%	25	A	A	A	A	A	A	A	A	C	A	C	C
	Hydrochloric acid 37%	80	A	A	A	A	A	A	A	C	D	C	D	D
	Sulfuric acid 98%	25	A	A	A	A	A	A	A	A	D	C	D	D
	Sulfuric acid 98%	80	A	A	A	A	A	A	A	D	D	D	D	D
	Fuming sulfuric acid	25	A	A	A	B	B	A	B	C	D	D	D	D
	Nitric acid 60%	25	A	A	A	A	A	A	A	A	D	D	D	D
	Nitric acid 60%	80	A	A	A	A	A	B	A	D	D	D	D	D
	Hydrofluoric acid 50%	25	A	A	A	A	A	A	A	A	D	D	D	D
	Glacial acetic acid	25	A	A	A	D	D	D	D	D	B	C	D	D
	Anhydrous acetic acid	25	A	A	A	D	D	D	D	D	C	A	D	D
	Phosphoric acid	25	A	A	A	A	A	A	A	A	C	A	D	D
	Phosphoric acid	80	A	A	A	A	A	A	A	A	D	A	D	D
	Formic acid	25	A	A	A	A	A	A	A	C	C	C	B	C
Aqua regia	25	A	A	A	A	A	A	A	B	D	D	D	D	
Alkalis	Sodium hydroxide 50%	25	A	A	A	A	A	A	A	A	-	A	-	-
	Sodium hydroxide 50%	80	A	A	A	A	A	A	A	D	D	A	-	D
	Hypochlorous acid 10%	25	A	A	A	A	A	A	A	A	D	A	D	D
	Aqueous ammonia 28%	25	A	A	A	B	B	B	B	D	A	A	D	A
	Ammonium fluoride	25	A	A	A	A	A	A	A	A	-	A	-	-
Alcohols	Methanol	25	A	A	A	A	A	A	A	D	A	A	A	A
	Ethanol	25	A	A	A	A	A	A	A	A	A	A	A	A
	Isopropyl alcohol	25	A	A	A	A	A	A	A	A	B	A	B	B
Amines	n-methyl-2- pyrrolidone	25	A	A	A	D	D	D	D	D	-	A	-	-
	Ethylene diamine	25	A	A	A	D	D	D	D	D	B	A	B	B
Aldehyde furan	Tetrahydrofuran	25	A	A	A	D	D	D	D	D	D	C	D	D
	Acetaldehyde	25	A	A	A	D	D	D	D	D	D	A	D	D
	Furfural	25	A	A	A	B	B	B	B	D	D	A	D	D

How to read evaluation symbols

A ... Percentage change of volume 0 – 10%	The external appearance is virtually unchanged. It is predicted that under severe pressure or temperature conditions the physical characteristics of the material will deteriorate slightly.
B ... Percentage change of volume 10 – 20%	The physical characteristics of the material deteriorate markedly, so the material cannot be recommended for dynamic applications.
C ... Percentage change of volume 20 – 40%	The physical characteristics deteriorate to an extreme degree, so the material is not recommended for dynamic applications. This material can sometimes be used for static applications over a short period of time.
D ... Percentage change of volume 40% or higher	The material cannot be used.

Inspected in NICHIAS

Chemicals		Temperature [°C]	NICHIAS original high performance elastomer							Standard materials				
			BLAZER™ NEXT	BLAZER™ S2	BLAZER™ A	BLAZER™ FC	BLAZER™ FE	PURE RUBBER™	FLUORO ELASTOMER FB	FLUORO ELASTOMER FA	Silicone elastomer	Ethylene propylene elastomer	Chloroprene elastomer	Nitrile elastomer
Ketone, ester, ether	Acetone	25	A	A	A	D	D	D	D	D	C	D	D	D
	Methyl ethyl ketone	25	A	A	A	D	D	D	D	D	D	D	D	D
	Methyl isobutyl ketone	25	A	A	A	D	D	D	D	D	D	D	D	D
	Butyl acetate	25	A	A	A	D	D	D	D	D	D	D	D	D
	Ethyl lactate	25	A	A	A	D	D	D	D	D	D	D	D	D
	Cyclohexanone	25	A	A	A	D	D	D	D	D	D	D	D	D
	Propylene glycol monomethyl ether	25	A	A	A	D	D	D	D	D	-	D	-	-
	Propylene glycol monomethyl ether acetate	25	A	A	A	D	D	D	D	D	-	D	-	-
Hydrocarbons	Cyclohexane	25	A	A	A	A	A	A	A	A	D	D	D	B
	Isooctane	25	A	A	A	A	A	A	A	A	D	D	D	A
	Benzene	25	A	A	A	A	A	A	A	C	D	D	D	D
	Toluene	25	A	A	A	A	A	A	A	C	D	D	D	D
Chlorine-based solvent	Chloroform	25	A	A	A	B	B	A	B	B	D	D	D	D
	Carbon tetrachloride	25	-	-	B	B	B	B	B	A	D	D	D	D
	Silicon tetrachloride	25	-	-	B	B	B	B	B	A	D	D	D	D
	Methylene chloride	25	A	A	A	B	B	C	B	D	D	D	D	D
	Trichloroethylene	25	A	A	A	B	B	B	B	C	D	D	D	D
Steam	Steam	150	A	A	A	A	A	D	A	B	D	-	D	D
	Steam	250	-	A	D	-	-	-	-	-	-	-	-	-
Other chemical related to semiconductor manufacture	Hexamethyldisilazane	25	A	A	A	A	A	A	A	A	-	-	-	-
	Piranha solution [H ₂ SO ₄ : H ₂ O ₂ = 3:1]	25	A	A	A	A	A	A	A	A	-	-	-	-
	SC-1 [NH ₄ OH (27%) : H ₂ O ₂ (30%): H ₂ O = 1 : 1 : 5]	25	A	A	A	A	A	A	A	A	-	-	-	-
	SC-2 [HCl(37%): H ₂ O ₂ (30%): H ₂ O = 1 : 1 : 6]	25	A	A	A	A	A	A	A	A	-	-	-	-
	BHF [HF-NH ₄ F-H ₂ O]	25	A	A	A	A	A	A	A	A	-	-	-	-
	DHF [HF-H ₂ O]	25	A	A	A	A	A	A	A	A	-	-	-	-

Physical properties of elastomer materials

NICHIAS original high performance elastomer

Type of material	NICHIAS product name	BLAZER™ NEXT	BLAZER™ S2	BLAZER™ A	PERFLUORO PFW™	BLAZER™ FC	BLAZER™ FE	PURE RUBBER™	FLUORO ELASTOMER FB	FLUORO PLUS
	NICHIAS material symbol	BNX	BS2	BA	PFW	BFC	BFE	TPFE	FB	FA-F
	Features	Heat resistance	Steam resistance	Chemical resistance	Plasma resistance	Plasma resistance	Plasma resistance	Ozone resistance and acid resistance	Steam resistance and acid resistance	Non-adhesiveness
JIS symbol	—	—	—	—	—	—	—	—	—	
Color	Black	Black	Black	White	Black	Black	Transparent	Black	Black	
Working temperature range (°C)	0~335	0~320	0~210	0~200	0~200	0~200	0~150	0~200	-15~200	
Normal physical properties	Type A durometer hardness	76	82	75	71	60	60	62	70	70
	Tensile strength (MPa)	11.1	27.5	13.1	9.8	18.8	11.4	17.3	15.7	16.6
	Elongation (%)	140	200	150	150	210	230	590	460	210
	100% tensile stress (MPa)	8.3	15.6	6.4	5.9	3.9	3.5	1.6	2.8	3.9
Compression set characteristics	Test conditions (Temperature in °C × Time in hrs)	300×72	300×72	150×72	200×72	100×72	100×72	100×72	175×24	175×72
	Compression set (%)	26	45	20	25	9	9	34	20	8
Aging resistance	Test conditions (Temperature in °C × Time in hrs)	—	—	—	230×24	—	—	—	230×24	230×24
	Type A durometer hardness change	—	—	—	-5	—	—	—	0	+2
	Tensile strength percentage change (%)	—	—	—	-6.5	—	—	—	-13.0	-13.0
	Elongation percentage change (%)	—	—	—	+4.5	—	—	—	-6.0	-15.5

Standard materials

Type of material	NICHIAS product name	FLUORO ELASTOMER FA	Silicone elastomer	Ethylene propylene elastomer	Chloroprene elastomer	Nitrile elastomer
	NICHIAS material symbol	FA	SI	EP	CR	NBR
	Features	Heat resistance	Heat resistance	Weather resistance and water resistance	Weather resistance and oil resistance	Mineral oil resistance
JIS symbol	FKM-70	VMQ-70	EPDM-70	—	NBR-70-1	
Color	Black	Reddish brown	Black	Black	Black	
Working temperature range (°C)	-15~200	-50~200	-40~150	-30~120	-30~120	
Normal physical properties	Type A durometer hardness	69	70	70	67	68
	Tensile strength (MPa)	15.3	6.3	15.3	12.8	16.4
	Elongation (%)	300	260	280	260	300
	100% tensile stress (MPa)	3.3	—	—	4.2	3.0
Compression set characteristics	Test conditions (Temperature in °C × Time in hrs)	200×72	175×72	100×72	100×72	120×72
	Compression set (%)	22	27	8	29	13
Aging resistance	Test conditions (Temperature in °C × Time in hrs)	230×72	230×72	100×72	100×72	120×72
	Type A durometer hardness change	+1	-6	+1	+9	+4
	Tensile strength percentage change (%)	-5	-8	+9	+8	-3
	Elongation percentage change (%)	±0	-23	+4	-23	-29

■ Test method

- Type A durometer hardness: JIS K 6253 (Elastomer, vulcanized or thermoplastic – Determination of hardness – Part 3: Durometer method)
- Tensile strength, elongation, 100% tensile stress: JIS K 6251 (Elastomer, vulcanized or thermoplastics – Determination of tensile stress-strain properties)
- Compression set: JIS K 6262 (Elastomer, vulcanized or thermoplastic – Determination of compression set at ambient, elevated or low temperatures)
- Thermal aging characteristics: JIS K 6257 (Elastomer, vulcanized or thermoplastic – Determination of heat ageing properties)

Product No. (TOMBO™ No.) indication method

NICHIAS product name	BLAZER™ NEXT	BLAZER™ S2	BLAZER™ A	PERFLUORO PFW™	BLAZER™ FC	BLAZER™ FE	PURE RUBBER™	FLUORO ELASTOMER FB	FLUORO PLUS	FLUORO ELASTOMER FA	Silicone elastomer	Ethylene propylene elastomer	Chloroprene elastomer	Nitrile elastomer
O-rings	2670 - BNX	2675 - S2	2675 - A	2670 - PFW	2675 - FC	2675 - FE	2670 - TPFE	2670 - FB	2670 - FA-F	2670 - FA	2670 - SI	2670 - EP	2670 - CR	2670 - NBR
Molded products other than O-rings	2680 - BNX	2685 - S2	2685 - A	2680 - PFW	2685 - FC	2685 - FE	—	2680 - FB	2680 - FA-F	2680 - FA	2680 - SI	2680 - EP	2680 - CR	2680 - NBR

* PURE RUBBER is used only for O-rings.

Allowable manufacturing dimensions

Product shape		Allowable manufacturing dimensions		Remarks
		Width × Length	Thickness	
O-rings		JIS B 2401 (P, G, V), AS 568 B, others		Regarding original high performance elastomer, dies of certain dimensions are not available, so please check when ordering.
Molded products other than O-rings		Various shapes and dimensions (drawing instructions)		
Elastomer sheet	High performance elastomer	300mm × 300mm	1.0, 1.5, 2.0, 3.0 (mm)	
	Standard elastomer	1000mm × 1000mm	1.0, 1.5, 2.0, 3.0 (mm)	

To ensure safe use

To ensure that the products in this catalog maintain their intended performance and can be used safely, be sure to strictly observe the following items.

- The physical properties and applications indicated in this catalog are representative properties and applications.
- The rough values of heat resistance indicated in this catalog are for reference only. They are not guaranteed values. Performance data is based on the results of tests performed by NICHIAS and also actual records obtained from general applications.
- These products are used in a variety of locations and equipment. The actual conditions of use differ from one application to another, so it is recommended that before using a product you carry out a test under the actual conditions of use.
- Concerning individual applications, it is necessary to evaluate each individual design and its suitability before selecting a product. For special applications, please contact us.
- The contents of this catalog may be changed without prior notice.



Precautions for handling products

Please observe the following cautions in order to maintain the intrinsic functions of the products and also to ensure that these products are used safely.

1. Do not use a product for any other purpose than the ones described in the catalog and specification, etc.
2. Store products indoor at ambient temperature and humidity to avoid direct rays, and strictly avoid to get wet.
3. This product is washed and packaged in a clean room. Therefore, to avoid adhering to contaminations, be sure to open the package just before using products.
4. Do not damage the surface of products.
5. Avoid twisting of products when installing.
6. For disposal, follow local regulations.

Head Office

6-1, Hatchobori 1-chome, Chuo-ku, Tokyo 104-8555, Japan
International Marketing and Sales Group
 Phone: 81-3-4413-1132 Fax: 81-3-3552-6108
 Web Site: <http://www.nichias.co.jp/>

Overseas Sales Companies
Indonesia
PT. NICHIAS SUNIJAYA

Panin Life Center, 2nd Floor, Room 205, Jl. Letnan Jenderal S. Parman
 Kav. 91, Jakarta 11420, Indonesia
 Phone: +62-21-56956207 Fax: +62-21-56956208/56956209

Malaysia
NICHIAS SOUTHEAST ASIA SDN. BHD.

Suite A1102, 11th Floor, West Wing, Wisma Consplant 2,
 No. 7, Jalan SS 16/1, 47500 Subang Jaya, Selangor Darul Ehsan, Malaysia.
 Phone: +60-3-5636-4067 Fax: +60-3-5636-4078

Singapore
NICHIAS SINGAPORE PTE. LTD.

25 International Business Park, #01-15/17 German Centre,
 Singapore 609916
 Phone: +65-6571-0830/0838 Fax: +65-6265-7681

Vietnam
NICHIAS VIETNAM CO., LTD

Room 12-K, 12Floor, Center Building,
 Hapulico Complex No1 Nguyen Huy Tuong,
 Thanh Xuan Trung, Thanh Xuan, Hanoi, Vietnam
 Phone: + 84-4-3791-7194 Fax: + 84-4-3791-6203

Thailand
NICHIAS (THAILAND) CO., LTD.

85 Moo 1, Wellgrow Industrial Estate T. Homsin, A. Bangpakong
 Chachoengsao 24180, Thailand
 Phone: +66-38-570-600 Fax: +66-38-570-601

THAI NICHIAS INTERNATIONAL CO., LTD.

Unit 1107, 11th Floor, AIA Capital Center
 89 Ratchadaphisek Road, Dindaeng, Dindaeng, Bangkok 10400 Thailand
 Phone: +66-2-001-2060 Fax: +66-2-001-2062

China
NICHIAS (SHANGHAI) TRADING CO., LTD.

霓佳斯（上海）贸易有限公司
 Room 1701, THE PLACE, Tower A, No. 100 Zun Yi Road,
 Changning District, Shanghai, P.R.China Postcode 200051
 中国上海市长宁区遵义路100号虹桥南丰城A栋1701室 邮编200051
 Phone: +86-21-6236-1783 Fax: +86-21-6236-1781

NICHIAS (SHANGHAI) TRADING CO., LTD. Guangzhou Branch

霓佳斯（上海）贸易有限公司 广州分公司
 17F-G, Gold Sun Building, No.109 Tiyu West Road, Guangzhou,
 Guang Dong Province, 510620, P.R.China
 中国广东省广州市天河区体育西路109号高盛大厦17楼G室 邮编 510620
 Phone: +86-20-3879-1640 Fax: +86-20-3879-1647

NICHIAS (SHANGHAI) AUTOPARTS TRADING CO., LTD.

霓佳斯（上海）汽车零部件贸易有限公司
 Room 1702, THE PLACE, Tower A, No. 100 Zun Yi Road,
 Changning District, Shanghai, P.R.China Postcode 200051
 中国上海市长宁区遵义路100号虹桥南丰城A栋1702室 邮编200051
 Phone: +86-21-6236-2668 Fax: +86-21-6236-2667

Germany
NICHIAS AUTOPARTS EUROPE GmbH

Prinzenallee 7, 40549 Düsseldorf, Germany
 Phone: +49 (0)211-52391-058 Fax: +49 (0)211-52391-200

United Kingdom
NICHIAS EUROPE (UK) LTD

10th Floor, Hardman Street, Manchester, M3 3HF, UK
 Phone: +44-0-161-932-1422 Fax: +44-0-161-932-1401

Overseas Construction Companies
Malaysia
NICHIAS SOUTHEAST ASIA SDN. BHD.

Suite A1102, 11th Floor, West Wing, Wisma Consplant 2,
 No. 7, Jalan SS 16/1, 47500 Subang Jaya, Selangor Darul Ehsan, Malaysia.
 Phone: +60-3-5636-4067 Fax: +60-3-5636-4078

Thailand
THAI-NICHIAS ENGINEERING CO., LTD.

45 Huaypong-Nongbon Road, Huaypong, Muang Rayong,
 Rayong Province 21150, Thailand
 Phone: +66-38-682-242 Fax: +66-38-691-156

Overseas Factories
Indonesia
PT. NICHIAS ROCKWOOL INDONESIA
PT. NICHIAS METALWORKS INDONESIA
Malaysia
NICHIAS FGS SDN. BHD.
NT RUBBER-SEALS SDN. BHD.
Vietnam
NICHIAS HAIPHONG CO., LTD.
China
SUZHOU NICHIAS INDUSTRIAL PRODUCTS CO., LTD.

(苏州霓佳斯工业制品有限公司)

SUZHOU NICHIAS SEAL MATERIAL CO., LTD.

(苏州霓佳斯密封材料有限公司)

SHANGHAI XINGSHENG GASKET CO., LTD.

(上海兴盛密封垫有限公司)

SHANGHAI GOYU AUTO PARTS CO., LTD.

(上海五友汽车零部件有限公司)

India
NICHIAS INDUSTRIAL PRODUCTS PRIVATE LTD.
Czech
NICHIAS AUTOPARTS EUROPE a.s.
Mexico
NAX MFG, S.A.DE C.V.
⚠ Cautions

- The products included in this catalog are intended for common use, including those presented in the catalog. If you intend to use any of the products in a way that requires extremely high quality and reliability such that any possible defect may directly affect the safety of human lives, please make sure to consult with our company in advance and take necessary measures at your responsibility.
- Because the stated material values may vary according to actual usage environments or circumstances, please consider such figures as indications for reference.
- The content of the catalog explains the features of the products when they are used alone. When actually using the products, please start using them after testing them under the actual usage environment.
- The content of the explanation of the products may be modified without any advance notice, and the production of the product may also be discontinued without advance notice. Please obtain the latest version of the catalog, and confirm the content thereof. The date of issuance of this catalog is printed in the upper left corner of this page.
- The standards, accreditation and provisions of laws included in the catalog may not conform with the latest version thereof.
- We strictly prohibit any acts of infringement upon our rights that are protected by the Copyright Act with regard to information included in the catalog, through the production of copies or imitations, misappropriation or unauthorized reprinting.
- Please be informed that, in the case where any problem involving a third party's industrial property right arises due to the use of any product included in the catalog, our company shall not be responsible for any problems other than the problems arising strictly due to reasons related to only such products.
- Please be aware that our company will not bear any responsibility for the following damage related to our products:
 - Damage arising due to natural disasters or accidents occurring for reasons that are not attributable to our company;
 - Damage arising due to remodeling, repairing or other acts by a third party;
 - Damage arising due to the willful intent or negligence of the customer or the user, or due to the improper use or use under abnormal conditions of the products;
 - Damage arising due to the failure to carry out regular checkups and appropriate repairs, maintenance and part replacements, considering various conditions, such as the usage conditions, usage environment and usage period, etc., of the product;
 - Indirect damage (including any operational damage, lost profits, opportunity losses, etc.) arising due to the use of or inability to use our company's product;
 - Damage arising due to a situation which was unforeseeable under the technical standards at the time of the shipment of our company's product; or
 - Damage arising due to reasons that are not attributable to our company.

